



批次	样品名称	生产日期	分析项目		
			Cu%	Ag(g/t)	Au(g/t)
3-4	粗铜	3.04	93.46	3592	14.30
3-8	粗铜	3.08	95.00	3070	14.30
10炉	粗铜	3.27	94.76	3411	10.90
11炉	粗铜	3.29	94.47	2763	13.70
6-6-2	粗铜	6.06	91.49	4085	13.70






编号	样品名称	取样日期	分析项目					
			Pb%	Cu%	Bi%	Sb%	Ag(g/t)	Au(g/t)
0123-3#-1	铜锭	1.24	0.021	97.23	0.020	1.93	2971	266.10
0421-3#-2	铜锭	4.22	0.066	97.22	0.11	0.70	967	270.40
0429-3#-1	铜锭	4.30	0.16	97.44	0.37	1.29	1280	1074.10
0505-3#-1	铜锭	5.06	2.03	93.16	2.79	1.11	1197	232.50
0522-3#-2	铜锭	5.24	0.035	96.71	0.042	2.33	2215	248.10





批次	样品名称	生产日期	分析结果			
			Pb%	Cu%	Ag(g/t)	Au(g/t)
F-23-1-6	浮渣熔炼炉高冰铜	1.07	12.47	51.03	2061	5.80
F-23-2-8	浮渣熔炼炉高冰铜	2.09	14.42	49.13	2012	5.00
F-23-2-22	浮渣熔炼炉高冰铜	2.23	13.80	52.75	1789	6.60
F-23-4-2	浮渣熔炼炉高冰铜	4.03	10.14	51.54	1731	5.60
F-23-4-15	浮渣熔炼炉高冰铜	4.16	10.99	48.45	1462	5.60
F-23-5-1	浮渣熔炼炉高冰铜	5.02	11.73	47.96	1355	6.60
F-23-5-14	浮渣熔炼炉高冰铜	5.15	10.67	44.87	1116	3.80



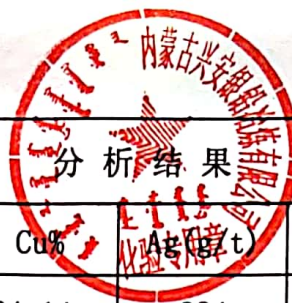

批次	样品名称	生产 日期	分析结果			
			Pb%	Cu%	Ag(g/t)	Au(g/t)
F-23-1-3	浮渣熔炼炉低冰铜	1.04	2.36	24.14	284	0.00
F-23-1-9	浮渣熔炼炉低冰铜	1.10	4.59	23.96	449	0.00
F-23-2-9	浮渣熔炼炉低冰铜	2.10	6.08	33.08	398	0.00
F-23-2-15	浮渣熔炼炉低冰铜	2.16	4.62	27.68	419	0.00
F-23-4-2	浮渣熔炼炉低冰铜	4.03	5.47	28.33	357	0.00
F-23-4-21	浮渣熔炼炉低冰铜	4.22	5.11	26.12	308	0.00
F-23-5-2	浮渣熔炼炉低冰铜	5.03	4.86	26.43	331	0.20
F-23-5-14	浮渣熔炼炉低冰铜	5.15	4.65	26.49	343	0.20





批次	样品名称	生产日期	分析结果				
			Pb%	Cu%	As%	Ag(g/t)	Au(g/t)
3-14-3	吹炼低冰铜	3.14	7.28	39.99	6.50	352	0.00
3-28-3	吹炼低冰铜	3.28	4.14	34.19	4.51	243	0.10
6-8-3	吹炼低冰铜	6.08	21.67	25.31	6.20	157	0.00
6-11-3	吹炼低冰铜	6.11	14.39	38.51	6.54	254	0.00
6-13-3	吹炼低冰铜	6.13	18.79	33.69	7.55	197	0.00

